

UNCLASSIFIED

REPORT CLASSIFICATION OF THIS PAGE

DTIC FILE COPY

(4)

REPORT DOCUMENTATION PAGE

AD-A201 596

1b RESTRICTIVE MARKINGS

2b. DECLASSIFICATION/DOWNGRADING SCHEDULE

3 DISTRIBUTION/AVAILABILITY OF REPORT

Approved for Public Release
Distribution Unlimited

4. PERFORMING ORGANIZATION REPORT NUMBER(S)

5 MONITORING ORGANIZATION REPORT NUMBER(S)

6a NAME OF PERFORMING ORGANIZATION
Department of Chemistry
University of North Carolina6b OFFICE SYMBOL
(if applicable)

7a NAME OF MONITORING ORGANIZATION

Office of Naval Research

6c ADDRESS (City, State, and ZIP Code)

Chapel Hill, North Carolina 27514

7b ADDRESS (City, State, and ZIP Code)

Department of the Navy
Arlington, VA 222178a NAME OF FUNDING/SPONSORING
ORGANIZATION8b OFFICE SYMBOL
(if applicable)

9 PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER

N00014-86-K-0608

3c ADDRESS (City, State, and ZIP Code)

10 SOURCE OF FUNDING NUMBERS

PROGRAM
ELEMENT NOPROJECT
NOTASK
NOWORK UNIT
ACCESSION NO

NR 053-617

11 TITLE (Include Security Classification) UNCLASSIFIED: Ferromagnetic Long Range Ordering In
Copper(II) Maleate Monohydrate

12 PERSONAL AUTHOR(S)

Juan Padilla, William E. Hatfield, John R. Wasson and William E. Estes

13a TYPE OF REPORT

Technical Report

13b TIME COVERED

FROM TO

14 DATE OF REPORT (Year, Month, Day)

11-20-88

15 PAGE COUNT

21

16 SUPPLEMENTARY NOTATION

Technical Report No. 33

17 COSATI CODES

FIELD	GROUP	SUB-GROUP

18 SUBJECT TERMS (Continue on reverse if necessary and identify by block number)

Heisenberg quadratic layer, Ferromagnetism superexchange,
low dimensional compounds, long range ordering,
carboxylate bridges, copper (II) maleate monohydrate

19 ABSTRACT (Continue on reverse if necessary and identify by block number)

The magnetic properties of copper(II) maleate monohydrate, $\text{Cu}(\text{C}_4\text{H}_2\text{O}_4) \cdot \text{H}_2\text{O}$, have been measured in the 1.8-66 K range. Magnetic susceptibility and isothermal magnetization measurements on powdered samples reveal a transition to a ferromagnetic state in this layered compound. The transition to the ordered state occurs at $T_C = 4.0$ K. The positive value of 8.0 K for the Weiss constant in the paramagnetic region confirms the ferromagnetic nature of the interactions. The magnetic susceptibility data above $3T_C$ may be fit with a Heisenberg quadratic layer expression with the best-fit parameters $J = +4.3/\text{cm}^{-1}$, $g = 2.0$, and $zJ' = +0.42/\text{cm}^{-1}$. The e.p.r. spectrum at room temperature indicates orthorhombic symmetry. A complex containing the isomeric form of the ligand, copper(II) fumarate dihydrate, has also been prepared and its magnetic properties determined in the 80-300 K range. The data may be accommodated by two-dimensional theory with $J = +1.05 \text{ cm}^{-1}$, $g = 2.09$, and $zJ' = +0.10 \text{ cm}^{-1}$.

20 DISTRIBUTION/AVAILABILITY OF ABSTRACT

☒ UNCLASSIFIED/UNLIMITED ☒ SAME AS RPT ☐ DTIC USERS

21 ABSTRACT SECURITY CLASSIFICATION

UNCLASSIFIED

22a NAME OF RESPONSIBLE INDIVIDUAL

22b TELEPHONE (Include Area Code)

22c OFFICE SYMBOL

OFFICE OF NAVAL RESERACH

Contract N000014-86-K-0608

R&T Code 413a001-000-01

TECHNICAL REPORT NO. 33

Ferromagnetic Long Range Ordering in

Copper(II) Maleate Monohydrate

by

Juan Padilla, William E. Hatfield, John R. Wasson,
and William E. Estes

The Department of Chemistry, The University of North
Carolina at Chapel Hill, North Carolina, 27599, U.S.A.

Prepared for publication in
Transition Metal Chemistry

Reproduction in whole or in part is permitted for
any purpose of the United States Government

*This document has been approved for public release
and sale, its distribution is unlimited.

*This statement should also appear in Item 3 of Document Control
Data - DD Form 1473. Copies of the form are available from the
cognizant contract administrator.

88 11 89 002



Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

Ferromagnetic long range ordering in copper(II) maleate monohydrate

Juan Padilla, William E. Hatfield*, John R. Wasson^(1a) and William E. Estes^(1b)

Department of Chemistry, The University of North Carolina at Chapel Hill,
Chapel Hill, North Carolina 27599-3290, USA

(Received 20 october 1988)

Summary

The magnetic properties of copper(II) maleate monohydrate, $\text{Cu}(\text{C}_4\text{H}_2\text{O}_4) \cdot \text{H}_2\text{O}$, have been measured in the 1.8-66 K range. Magnetic susceptibility and isothermal magnetization measurements on powdered samples reveal a transition to a ferromagnetic state in this layered compound. The transition to the ordered state occurs at $T_C = 4.0$ K. The positive value of 8.0 K for the Weiss constant in the paramagnetic region confirms the ferromagnetic nature of the interactions. The magnetic susceptibility data above $3T_C$ may be fit with a Heisenberg quadratic

*Author to whom all correspondence should be directed.

layer expression with the best-fit parameters $J = +4.3 \text{ cm}^{-1}$, $g = 2.0$, and $zJ' = +0.42 \text{ cm}^{-1}$. The e.p.r. spectrum at room temperature indicates orthorhombic symmetry. A complex containing the isomeric form of the ligand, copper(II) fumarate dihydrate, has also been prepared and its magnetic properties determined in the 80-300 K range. The data may be accommodated by two-dimensional theory with $J = +1.05 \text{ cm}^{-1}$, $g = 2.09$, and $zJ' = +0.10 \text{ cm}^{-1}$.

Introduction

As part of our program devoted to the identification and characterization of insulating ferromagnets, we have studied the magnetic properties of copper(II) maleate monohydrate (Cu-Mal), since the x-ray structural results⁽²⁾ show carboxylate bridging of the type found in copper(II) compounds with ferromagnetic interactions. The copper(II) ion in Cu-Mal has square pyramidal coordination. As shown in Figure 1, the apical ligand is a water molecule located at 2.26 Å, and the donor atoms in the square plane are two oxygen atoms of a single maleate chelating ligand, and two oxygen atoms from two additional different maleate groups. The copper-oxygen bonds in the square plane are equal in length (1.99 Å), and the cis-oxygen atoms are at right angles. Each maleate group is bonded to three different copper atoms forming a polymeric sheet. The copper maleate sheets are linked by hydrogen bonds (2.79 Å) between the water molecule and the carboxyl oxygen atom⁽²⁾, as indicated by the dashed lines in Figure 1. The shortest Cu-Cu distance within a layer is 5.12 Å, and the shortest Cu-Cu distance between two adjacent layers is 5.98 Å. Results of our magnetic studies on Cu-Mal, which show interactions in

the plane followed by long range ordering, are described here. Magnetic data for copper(II) fumarate dihydrate (Cu-Fum), are also presented. This latter compound was included in the study since the fumarate and maleate ligands are related by being trans- and cis- isomers, respectively.

Experimental

Synthesis

Maleic acid (10 g) (Chemical Dynamics Corp., South Plainfield, N.J.) was dissolved in distilled H₂O (200 mL) and NaOH (6.9 g) was added slowly with stirring. Copper(II) chloride dihydrate (14.7 g), dissolved in hot water (200 mL), was then slowly added to the sodium maleate solution with vigorous stirring. After cooling to room temperature the blue precipitated product was isolated by filtration, washed with a little cold water and air dried. The yield was almost quantitative. Copper(II) fumarate dihydrate was prepared in a similar way. Elemental analysis was done by Galbraith Laboratories, Knoxville, TN. Found: C, 24.3; H, 2.2; Cu, 32.6. CuC₄H₄O₅ (Cu-Mal) calcd.: C, 24.6; H, 2.1; Cu, 32.5%. Found: C, 22.5; H, 3.0; Cu, 30.0. CuC₄H₆O₆ (Cu-Fum) calcd.: C, 22.5; H, 2.8; Cu, 29.8.

Magnetic measurements

Magnetic susceptibility measurements for Cu-Mal were determined in the 1.8 to 66 K range by using a vibrating sample magnetometer (VSM)^(3,4) at different magnetic fields (10,000, 100, and 2 Oe). The VSM magnetic field was calibrated against n.m.r. resonances (¹H and ³Li). Magnetization was measured as a function of the applied magnetic field (50 to 15,000 Oe) both above and below the transition temperature to

the ordered state. Magnetic susceptibility measurements for Cu-Fum were determined in the 80-300 K range using a Faraday type balance consisting of a Cahn 2000 electrobalance equipped with an Anac 3472 HA electromagnet and 502 Lewis coils from George Associates, Berkeley, CA. E.p.r. spectra were recorded with a Varian E-109 spectrometer operated at X-band frequency. The free-radical DPPH ($g = 2.0023$) was used as a field marker. The TIP correction for copper(II) was taken as $+ 60 \times 10^{-6}$ cgsu, and the diamagnetic corrections for constituent atoms in Cu-Mal and Cu-Fum were obtained by using Pascal's constants⁽⁵⁻⁷⁾.

Results

The effective magnetic moment data as a function of temperature for a powdered sample of Cu-Mal are shown in Figure 2. The magnetic moment increases from 1.9 B.M. at 66 K to almost 4.4 B.M. at 5.9 K. The increase at low temperatures strongly suggests a ferromagnetic interaction. The magnetic susceptibility data collected at 10,000 Oe in the 12 K range (i.e. $3T_C$) to 66 K may be fit by the Curie-Weiss law $\chi = C/(T - \theta)$, where $C = Ng^2\mu_B^2S(S+1)/3k$, with the best fit parameters $g = 2.11$ and $\theta = 8.0$ K. The positive value for the Weiss constant is also indicative of ferromagnetic interactions in Cu-Mal.

Since small values of the applied magnetic field affect the ferromagnetic properties, the transition temperature was determined from data collected with a very low applied magnetic field ($H = 2$ Oe). The Curie temperature, 4.0 K, was estimated to be the point of maximum slope in the plot of the magnetic susceptibility versus temperature data given in Figure 3.

The temperature dependence of the magnetization is shown in Figure

4 at 11 K, 4.2 K, and 2.5 K. The plot shows saturation of the magnetization at very low applied magnetic fields and confirms the presence of ferromagnetism.

In view of the layered structure of Cu-Mal and the nearly quadratic lattice ($a/b = 1.11$), it was anticipated that the magnetic properties could be explained by using the theoretical expansion developed by Baker for a square lattice structure⁽⁸⁾. The exchange Hamiltonian for a two-dimensional Heisenberg ferromagnet is given by Equation (1)

$$H = -2J \sum S_i \cdot S_j \quad (1)$$

where \sum runs over all pairs of nearest neighbor spins i and j . The Baker power series expansion is given by Equation (2)

$$X_B = Ng^2\mu_B^2 / kT [1 + \sum (\alpha_n / 2^n n!) x^n] \quad (2)$$

where $x = J/kT$, and the coefficients α_n for $n < 11$ for the square lattice have been tabulated⁽⁸⁾.

The expression for two-dimensional interactions was modified to account for the presence of magnetic interlayer interactions, by adding a mean-field term to give the expression (3)

$$X_M = X_B / (1 - 2zJ'X_B / Ng^2\mu_B^2) \quad (3)$$

where X_M is the corrected molecular field value of the molar susceptibility, X_B is the calculated magnetic susceptibility of an isolated layer given by Baker's expansion, z is the number of nearest neighbors in the layer, and J' is the interlayer exchange-coupling

constant. Expression (3) was fit to the experimental data by using a non-linear Simplex fitting numerical technique^(9,10). During the fitting the parameters J , J' , and g were allowed to vary freely.

The Baker expansion is valid only at temperatures well above the transition to the ordered state. This common limitation of high-temperature series expansions is a direct consequence of having a limited number of coefficients in the expansion. The experimental data were fitted for the temperature range with $J/kT < 0.6$ (11-66 K). The best fit to the Baker expansion model was obtained with an intralayer exchange coupling constant of $J = +4.3 \text{ cm}^{-1}$, an interlayer exchange coupling constant of $zJ' = +0.42 \text{ cm}^{-1}$, and $g = 2.00$. Fitting of the data without the mean-field term zJ' resulted in an even lower g -value (1.98).

The e.p.r. spectrum of Cu-Mal, shown in Figure 5, reveals anisotropic g -values with $g_1 = 2.25$, $g_2 = 2.18$, and $g_3 = 2.07$. These values are similar to those frequently seen in copper(II) compounds with orthorhombic symmetry. The average g -value of 2.17 from the e.p.r. measurements is somewhat larger than the g -value obtained from the analysis of the magnetic data with the Baker's expression or with the Curie-Weiss law.

When the average e.p.r. g -value of 2.17 was kept constant during the fitting routine, and J and J' were allowed to vary freely, J was found to be very close to zero, and zJ' was unreasonably high. Similarly, keeping constant the g -value of 2.11, obtained from the Curie-Weiss fit, led to the unreasonable result of interlayer interactions stronger than intralayer interactions.

The experimental data could also be fitted to a three-dimensional Heisenberg model⁽¹¹⁾ for body-centered and face-centered cubic lattices. When zJ' was not included, for the body-centered lattice the best fitting parameters were $J = 1.75 \text{ cm}^{-1}$ and $g = 2.05$, and for the

face-centered lattice $J = 1.11 \text{ cm}^{-1}$ and $g = 2.06$. Addition of the interlayer interaction parameter resulted in negative values for zJ' : -1.31 cm^{-1} for the body-centered, and -1.54 cm^{-1} for the face-centered lattice. However, the magnetic data reflect ferromagnetic interlayer interactions.

We also measured the magnetic susceptibility of copper(II) fumarate dihydrate in the temperature range 80-300 K using the Faraday balance. Fitting of the data to a Curie-Weiss equation yielded the best fitting parameters $g = 2.09$ and $\theta = +3.2 \text{ K}$. Fits to a square lattice using Baker's expansion yielded values for the parameters $J = +1.15 \text{ cm}^{-1}$, and $g = 2.09$. Inclusion of the mean-field term zJ' resulted in the following parameters: $J = +1.05 \text{ cm}^{-1}$, $g = 2.09$, and $zJ' = +0.10 \text{ cm}^{-1}$. The positive values for θ and J are indicative of ferromagnetic exchange interactions. The e.p.r. spectrum of Cu-Fum shows axial symmetry with $g_{\perp} = 2.12$ and $g_{\parallel} = 2.21$ at room temperature, and $g_{\perp} = 2.09$ and $g_{\parallel} = 2.18$ at 77 K. Unfortunately, no crystal structure has been reported for Cu-Fum and we will not speculate on the nature of the exchange.

Discussion

Fittings of the magnetic susceptibility data can not distinguish between the two-dimensional quadratic lattice and three-dimensional cubic lattices for Cu-Mal; however, the structural information favors the two-dimensional assignment. The ferromagnetism observed can be accounted for in terms of the square basal plane around copper and the carboxylate groups of the maleate chelate ligand. The $\sigma^* (d_{x^2-y^2})$ in-plane orbital on copper is properly situated for interactions with the orbitals of the carboxylate bridges permitting ferromagnetic spin-spin

coupling by superexchange. The dihedral angle between the planes defined by the carboxylate oxygen atoms bonded to copper ions within a layer, which is designated τ in Figure 1, was calculated by using a computer program⁽¹²⁾ and found to be 77.5° . This angle allows an almost orthogonal orbital pathway, and promotes the ferromagnetic nature of the interactions. There is a second pathway for superexchange through the 7-membered rings, but it is unlikely to make a significant contribution to the superexchange.

Ferromagnetic intralayer interactions predominate in the layer of Cu-Mal, but there are additional interlayer ferromagnetic couplings. These weaker interlayer interactions, which were accounted for through the addition of a mean-field term to the magnetic susceptibility expression, lead to the long range three-dimensional ordering.

From molecular field theory for ferromagnets⁽¹³⁾ the effective intralayer exchange field may be calculated from the following expression

$$H_{ex} = 2zJS/g\mu_B \quad (4)$$

Using the parameters determined in this study, an exchange field equal to 0.92×10^5 Oe was obtained. With data from a powdered sample, it is not possible to determine the in-plane anisotropy. Assuming axial symmetry, the out-of-plane anisotropy may be estimated from the magnetization data. By plotting dM/dH versus field⁽¹⁴⁾, this was determined to be about 1000 Oe.

Superexchange by carboxylate bridges

Copper(II) oxydiacetate hemihydrate⁽³⁾ is an example of a compound with carboxylate bridges that shows ferromagnetic behavior. The intralayer exchange coupling constant $J = +4.66 \text{ cm}^{-1}$ is very close to the exchange coupling constant obtained for Cu-Mal. This indicates that the oxydiacetate ligands transmit ferromagnetic intralayer interactions as effectively as the maleate groups.

By contrast, the out-of-plane anisotropy field (which is largely the interlayer exchange field) of copper(II) oxydiacetate hemihydrate is only 250 Oe. The much greater value of 1000 Oe for Cu-Mal reflects the presence of additional interlayer ferromagnetic interactions. This is in agreement with the structural features of both compounds. In copper(II) oxydiacetate hemihydrate the atoms in adjacent layers are held together by van der Waal's forces only, whereas in Cu-Mal the copper sheets are linked by hydrogen bonds. Hydrogen bonds provide a better pathway for interlayer exchange.

Copper(II) formate dihydrate (CuFUH)⁽¹⁵⁾ provides an example of a nearly Heisenberg layer antiferromagnet with carboxyl bridges. CuFUH has two unequivalent copper(II) ions in the unit cell linked by formate molecules to make up a square lattice structure. This compound with $J = -22.9 \text{ cm}^{-1}$ shows a magnetic phase transition to an antiferromagnetically long-range ordered state at 15.5 K. The exchange parameter was obtained from a fit of the data to a high-temperature series expansion using a two-dimensional Heisenberg model for a quadratic lattice. It is clear the formate ligands provide a strong pathway for antiferromagnetic exchange as evidenced by the large exchange coupling constant and the transition temperature.

Copper(II) hydrogen maleate tetrahydrate (Cu-MTH)⁽¹⁶⁾ is a closely related compound that also shows ferromagnetic interactions. Even

though the maleate ion is common to both compounds, the magnetic parameters are substantially different in magnitude as a result of significant structural differences. Cu-MTH has an intralayer constant $J = 0.6 \text{ cm}^{-1}$ with $zJ' = -0.2 \text{ cm}^{-1}$. The intralayer constant in Cu-MTH is notably weaker compared to Cu-Mal because the maleate ligands are not directly bonded to the copper ions in Cu-MTH. Instead, the copper ion is bonded to six water molecules, and bonding to maleate ions occur through hydrogen bonds. While the water bridges provide a superexchange pathway, they are not as effective as the maleate bridges in Cu-Mal.

In conclusion, we have found the short-range ordering effects within the layer structure in Cu-Mal dominate the magnetic susceptibility down to the transition temperature, where the effects of the interlayer exchange and the anisotropy initiate the three-dimensional ferromagnetic ordering that occurs below 4.0 K. Below the transition temperature, the ferromagnetically ordered layers are coupled ferromagnetically through the hydrogen bonds.

Acknowledgments

This work was supported in part by the Office of Naval Research. J.P. thanks the Consejo Nacional de Ciencia y Tecnologia for a partial fellowship.

References

- 1a) SYNTHECO, Inc., 1920 Industrial Pike, Gastonia, N.C. 28052.
- 1b) E. I. Dupont de Nemours, Research Triangle Park, N.C.
- 2) C. K. Prout, J.R. Carruthers and F. J. C. Rossotti, J. Chem. Soc. (A), 3342 (1971).
- 3) P. J. Corvan, W. E. Estes, R. R. Weller and W. E. Hatfield, Inorg. Chem., 19, 1297 (1980).
- 4) D. B. Brown, V. H. Crawford, J. W. Hall and W. E. Hatfield, J. Chem. Phys., 81, 1303 (1977).
- 5) B. N. Figgis, and J. Lewis, In "Modern Coordination Chemistry"; J. Lewis and R. G. Wilkins (Eds.), Interscience: New York, 1960; Chapter 6, p. 403.
- 6) E. Konig, "Magnetic Properties of Transition Metal Compounds"; Springer-Verlag; West Berlin, 1956.
- 7) R. R. Weller and W. E. Hatfield, J. Chem. Ed., 56, 652 (1979).
- 8) G. A. Baker, H. E. Gilbert, J. E. Rushbrooke and G. S. Rushbrooke, Phys. Lett., 25A, 207 (1967).
- 9) M. S. Cacesi and W. P. Cacheris, Byte, May, 340 (1984).
- 10) J. A. Nelder and R. Mead, Computer Journal, 7, 308 (1965).
- 11) G. S. Rushbrooke, and P. J. Wood, Mol. Phys., 1, 257 (1958).
- 12) B. R. Rohrs, unpublished results.
- 13) J. S. Smart, "Effective Field Theories of Magnetism", W. B. Saunders Co. Philadelphia, 1966; Chapter 3.
- 14) D. B. Losee and W. E. Hatfield, Phys. Rev. B, 10, 1122 (1974).
- 15) Y. Yamamoto, M. Matsuura, and T. Haseda, J. Phys. Soc. Japan, 40, 1300 (1976).
- 16) L. W. ter Haar and W. E. Hatfield, Mol. Cryst. and Liq. Cryst., 107, 171 (1984).

Captions for the figures


Figure 1. Crystal structure of copper(II) maleate monohydrate showing the hydrogen bond (dashed lines) between adjacent layers. Note that this is an eight-formula unit segment of a polymeric sheet.


Figure 2. Temperature dependence of the effective magnetic moment per copper atom for Cu-Mal. The solid curve represents the best-fit to the experimental data using the parameters $J = +4.3 \text{ cm}^{-1}$, $zJ' = +0.42 \text{ cm}^{-1}$, and $g = 2.00$.


Figure 3. Plot of the magnetic susceptibility versus temperature for Cu-Mal taken at 100 Oe (squares), and 2 Oe (plus signs).


Figure 4. Isothermal magnetization data collected above and below the transition temperature to the ordered state. Squares, $T = 11 \text{ K}$; plus signs, $T = 4.2 \text{ K}$; rhombs, $T = 2.5 \text{ K}$.


Figure 5. E.p.r. spectrum of Cu-Mal in the solid state recorded at room temperature.

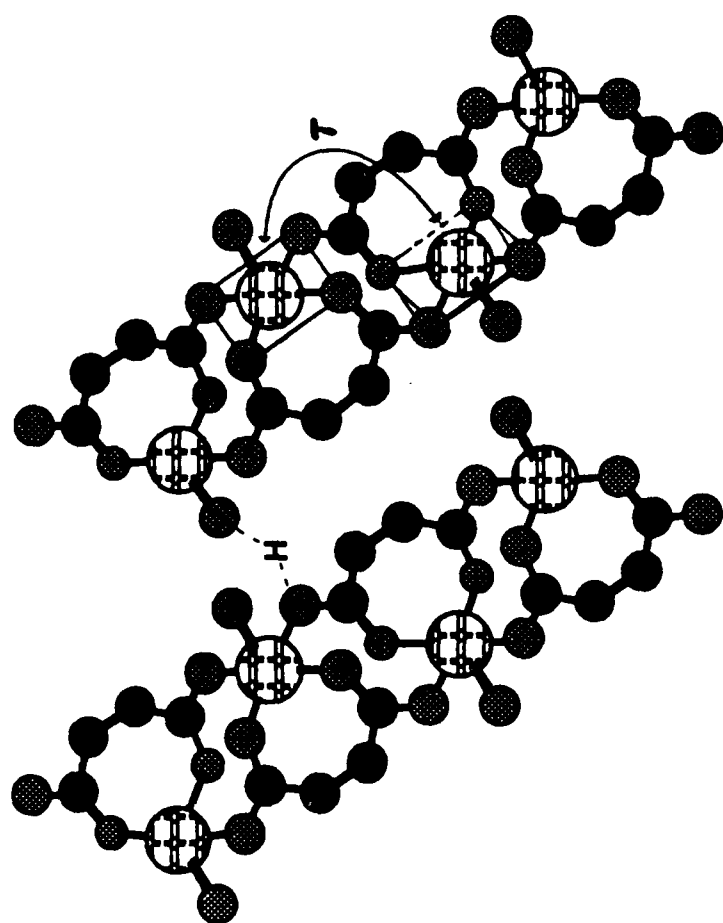

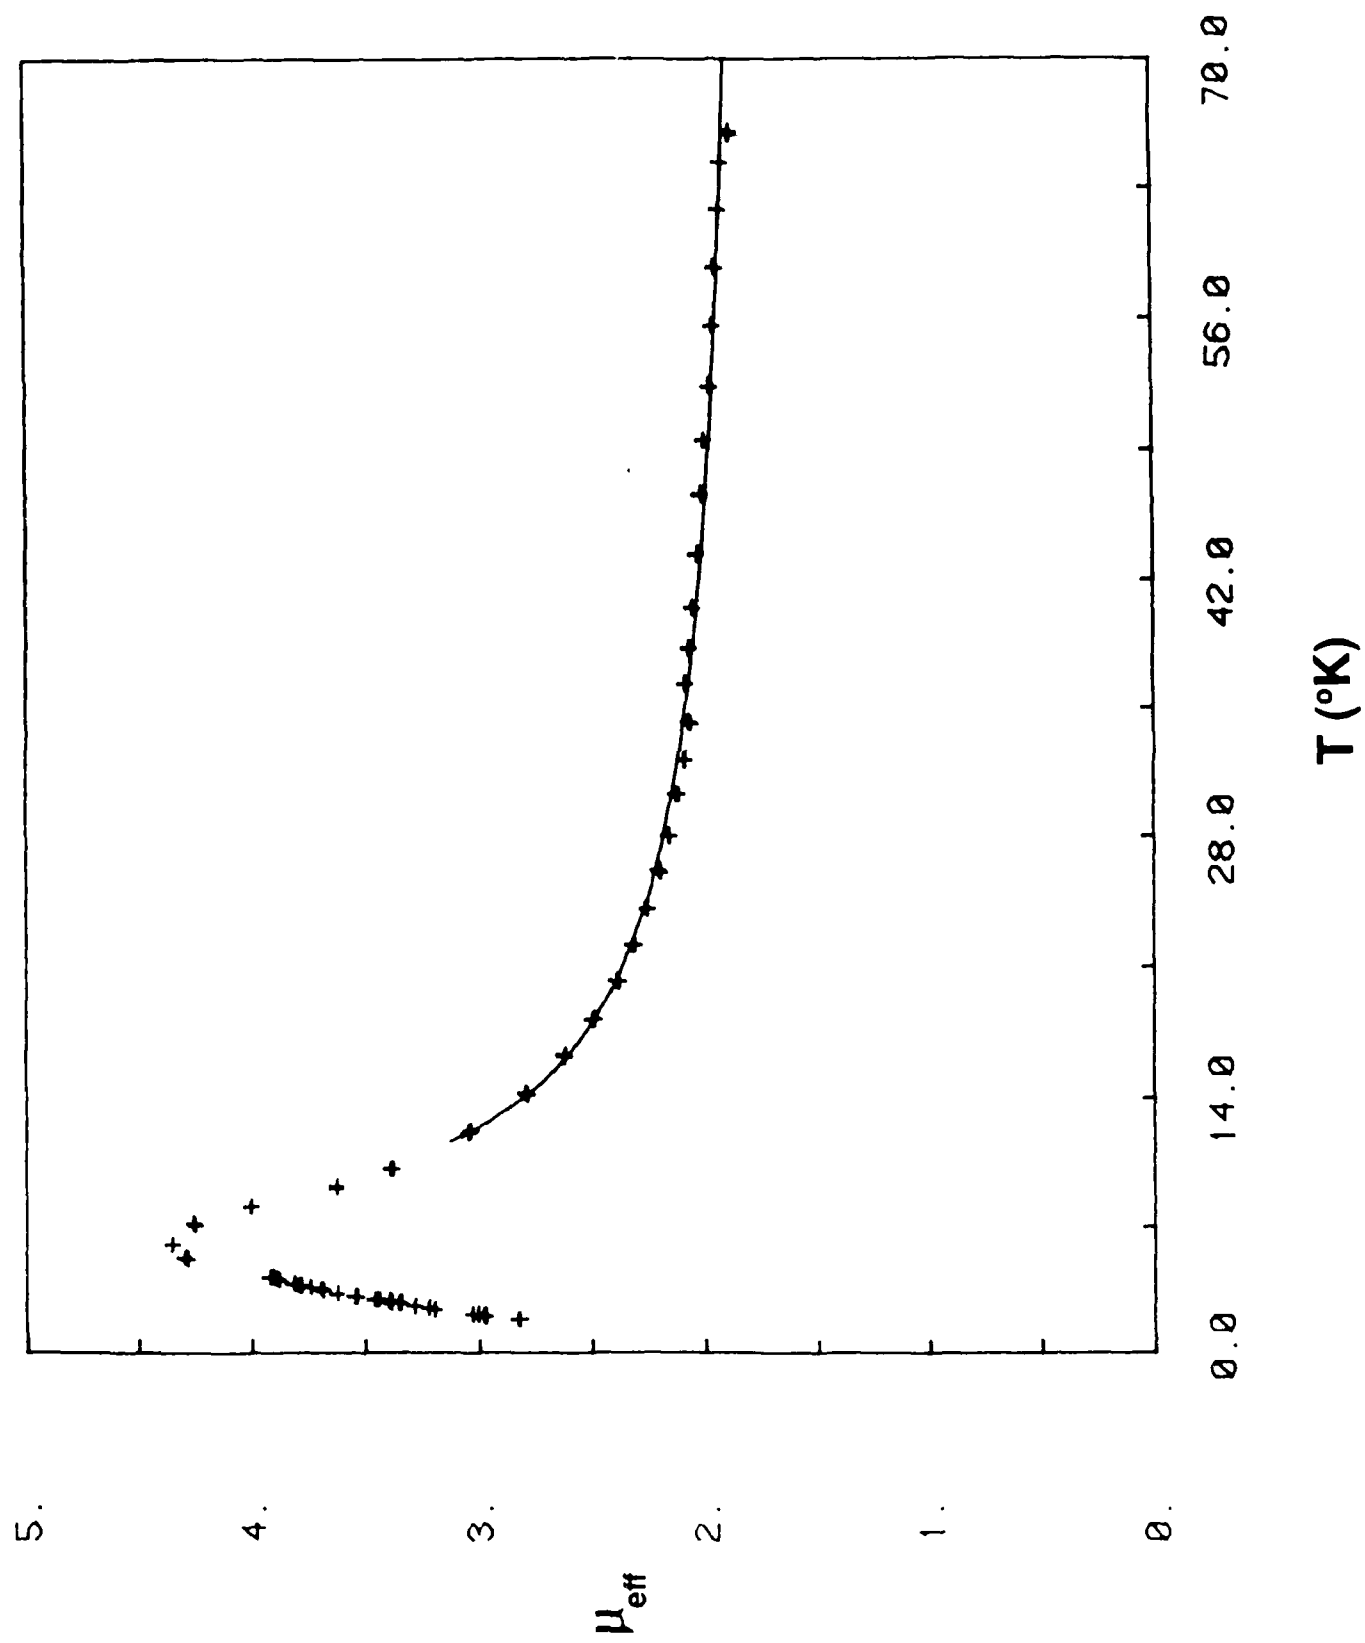

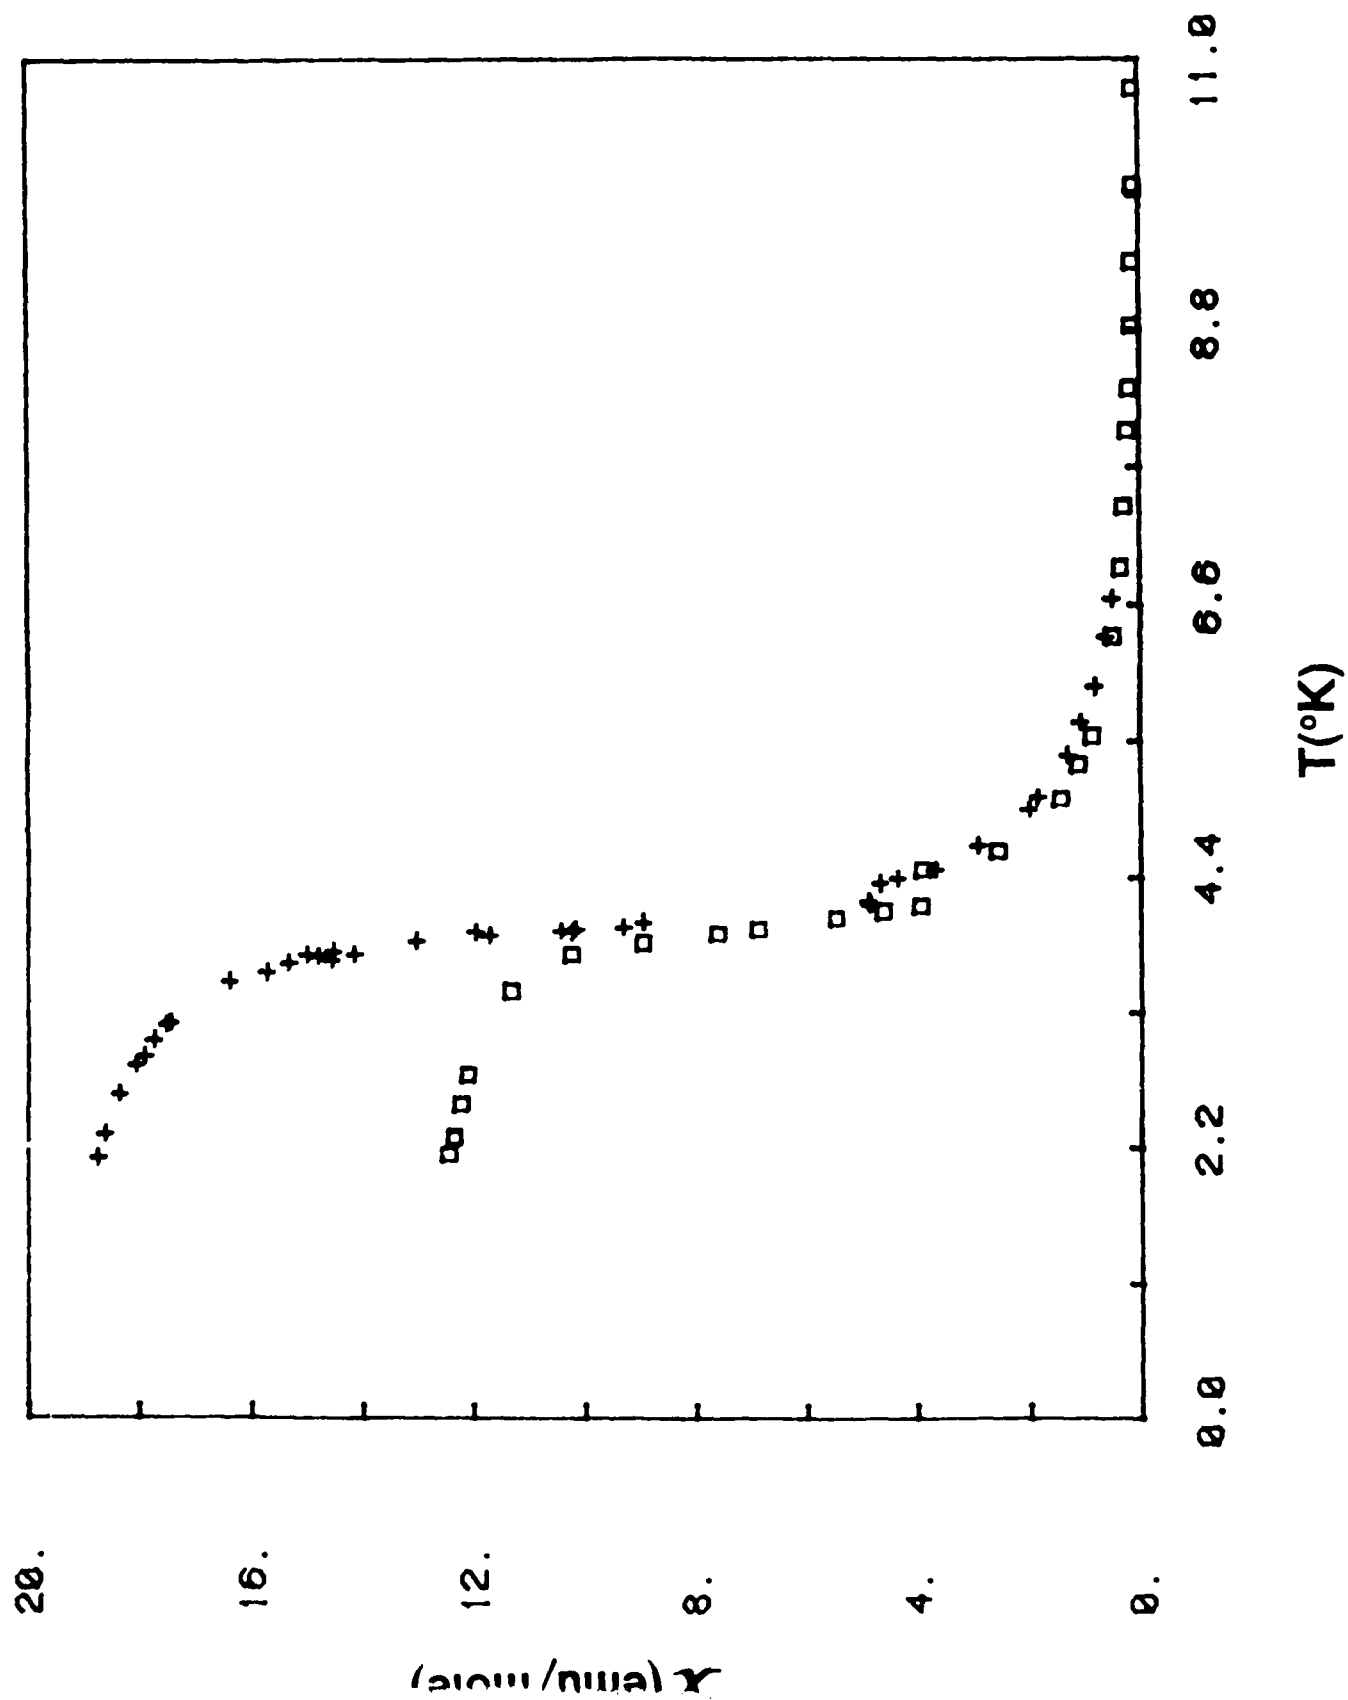

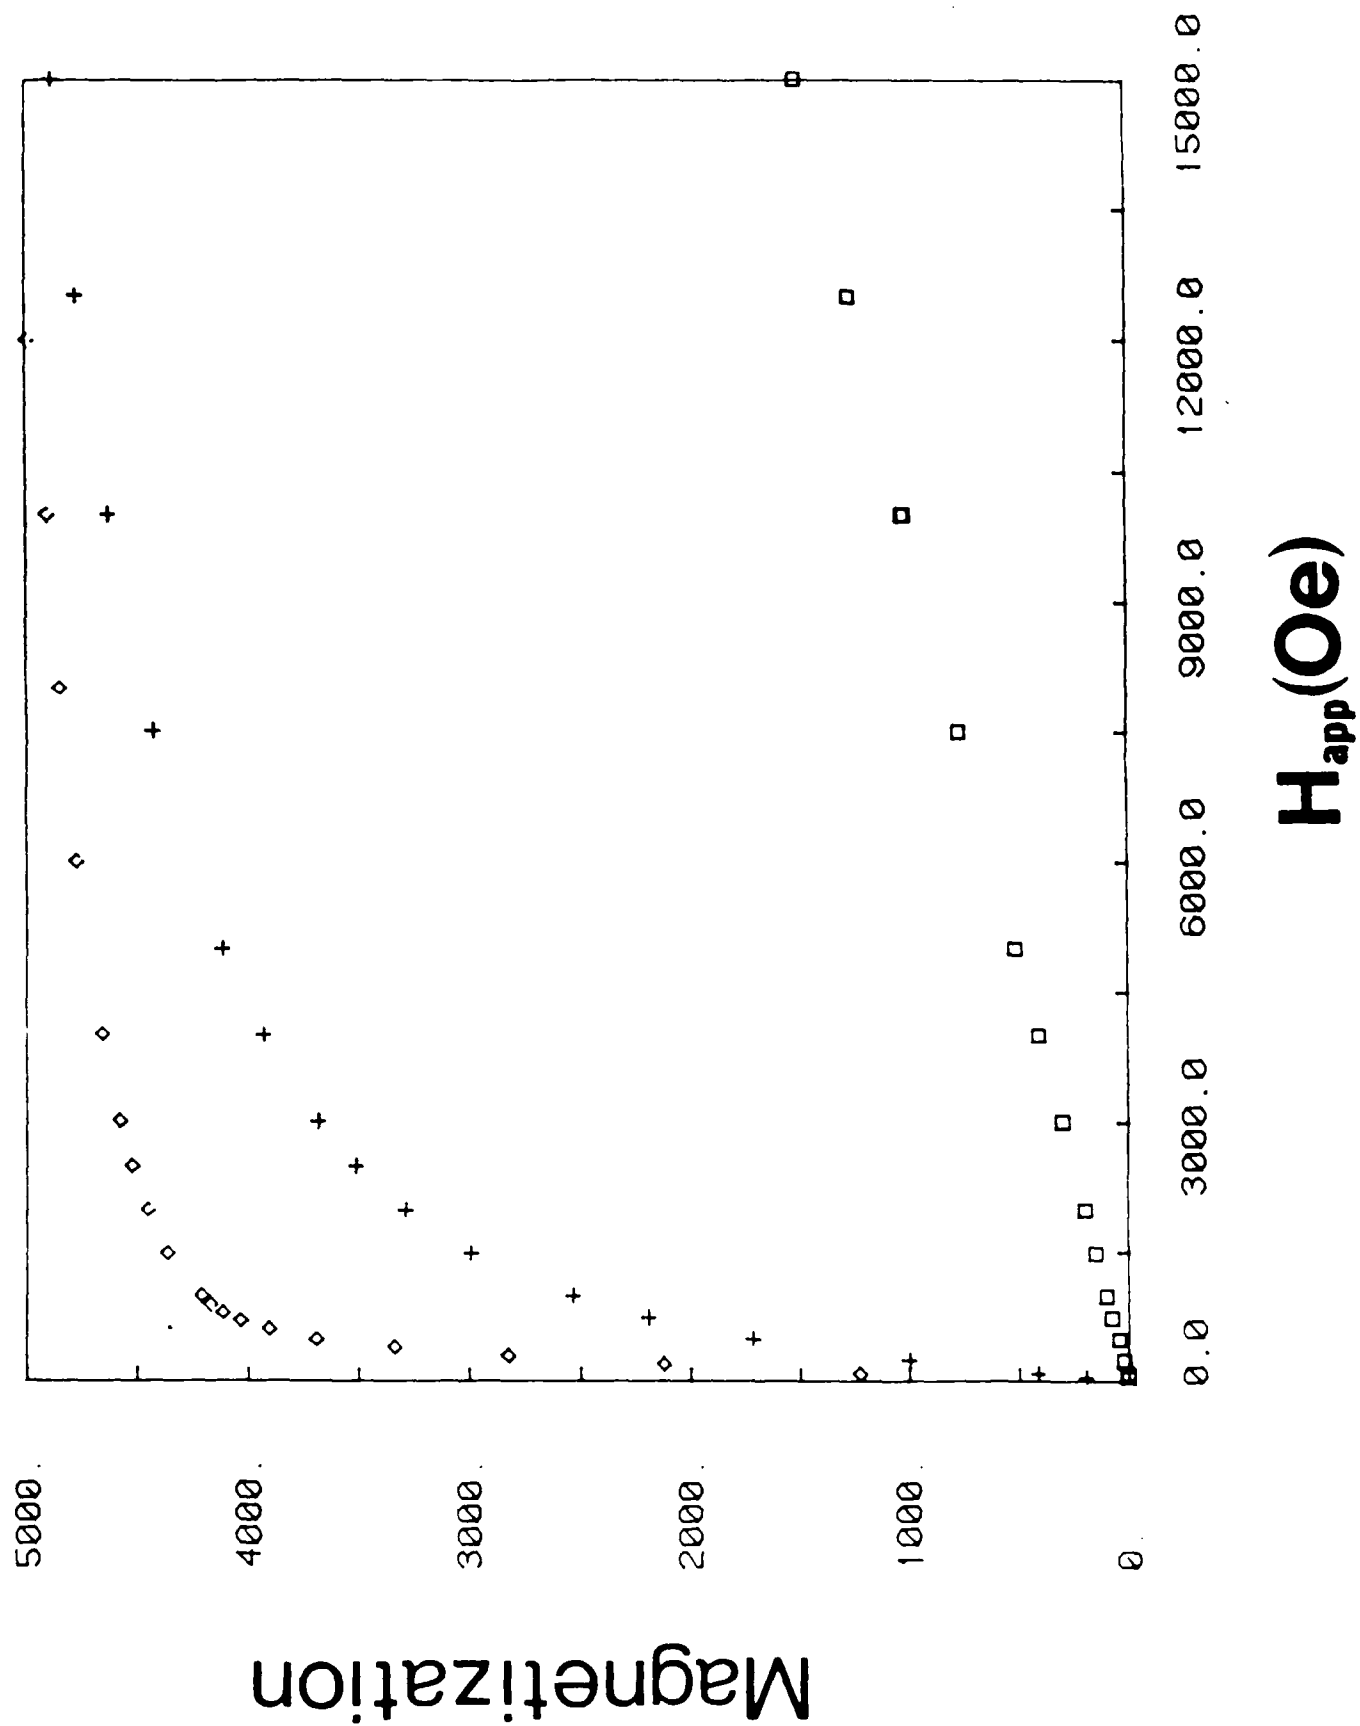

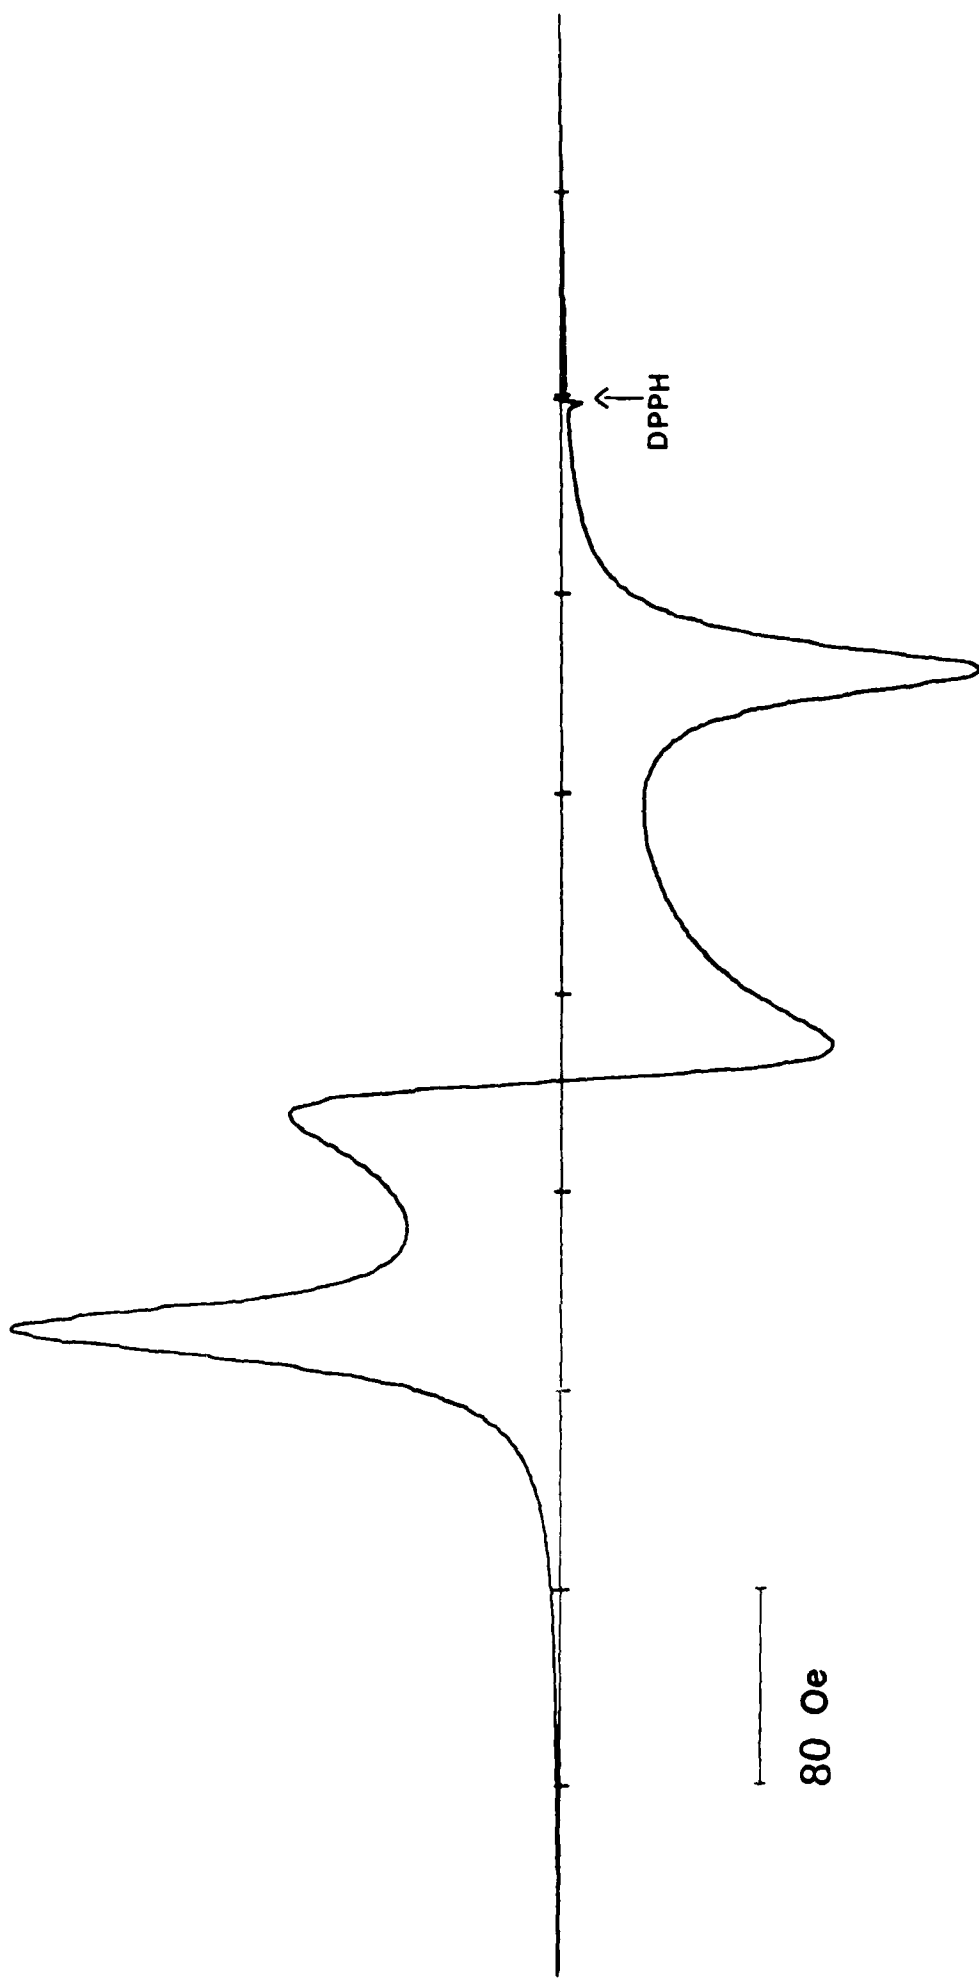

190-

DL/1113/87/2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code LS2 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1

ABSTRACTS DISTRIBUTION LIST 053

D/1113/87/2

Dr. M. F. Hawthorne
Department of Chemistry
University of California
Los Angeles, California 90024

Professor O. T. Beachley
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. W. Hatfield
Department of Chemistry
University of North Carolina
Chapel Hill, North Carolina 27514

Professor R. Wells
Department of Chemistry
Duke University
Durham, North Carolina 27706

Professor K. Neidenzu
Department of Chemistry
University of Kentucky
Lexington, Kentucky 40506

Dr. Herbert C. Brown
Department of Chemistry
Purdue University
West Lafayette, IN 47907

Dr. J. Zuckerman
Department of Chemistry
University of Oklahoma
Norman, Oklahoma 73019

Professor R. Neilson
Department of Chemistry
Texas Christian University
Fort Worth, Texas 76129

Professor M. Newcomb
Department of Chemistry
Texas A&M University
College Station, Texas 77843

Professor L. Miller
Department of Chemistry
University of Minnesota
Minneapolis, Minnesota 55455

Professor K. O. Christe
Rockwell International
Canoga Park, California 91304

Dr. Margaret C. Etter
Department of Chemistry
University of Minnesota
Minneapolis, MN 55455